



**Building
something
great**

TEST REPORT – CURING COMPOUND

CLIENT: EVENRANGE PTY LTD

ADDRESS: 12 Frankston Gardens Drive, Carrum Downs, VIC 3201

FILE NO: 258/26
REQUEST NO: 125269

LAB. SAMPLE NO: 339828

TEST METHOD: AS 3799 – 1998 - Liquid Membrane-forming Curing Compounds for Concrete

DISTRIBUTOR: PARCHEM

SAMPLE IDENTIFICATION: CONCURE X90 WHITE

SAMPLE DESCRIPTION: Water based Hydrocarbon resin curing compound

CLASSIFICATION: CLASS B, TYPE 2

SAMPLE SOURCE: VIC

DATE SAMPLED: UNKNOWN

DATE RECEIVED: 29/06/2026

METHOD OF APPLICATION: by spraying at standard application rate of 5 m²/L.

TEST RESULTS:

Standard property, Test (Method)	Specification	Result	Date Tested
Water retention efficiency AS 3799.3.1.2 (Appendix B)	Min. 90%	95%	24-27/07/2026
Non - volatile content* AS 3799.3.1.8 (Method AS 1580.301.1)	N / A	44.24%	22/07/2026
Density* AS 3799.3.1.9 (Method AS/NZS 1580.202.1)	N / A	0.990 kg/L	15/07/2026
Viscosity* AS 3799.3.1.5 (Method AS/NZS 1580.214.5)	Min. 0.05 Pa.s (emulsions) Min. 0.02 Pa.s (solutions)	0.24 Pa.s	30/07/2026
Drying Time* AS 3799.3.1.4 (Appendix C)	Max. 4 Hrs	2.5 Hrs	24/07/2026
Infrared absorption spectrum* AS 3799.3.2 (Boral In-house Method)	N / A	Attached	03/08/2026
Stability of emulsion* TfNSW T862	Max. 4%	0.13%	28/07/2026
Residue 150µm* AS 3799.3.1.6 (Method AS/NZS 2341.26)	Max. 0.2%	0.2%	23/07/2026

Notes:

- Sample was provided by the client and tested as received.
- * Test method is not in the current scope of NATA Accreditation for the Boral MTS laboratory.


Approved signatory

Sam El-Hamawi

Date 31/07/2026

Serial no. CEM125269.SE.2



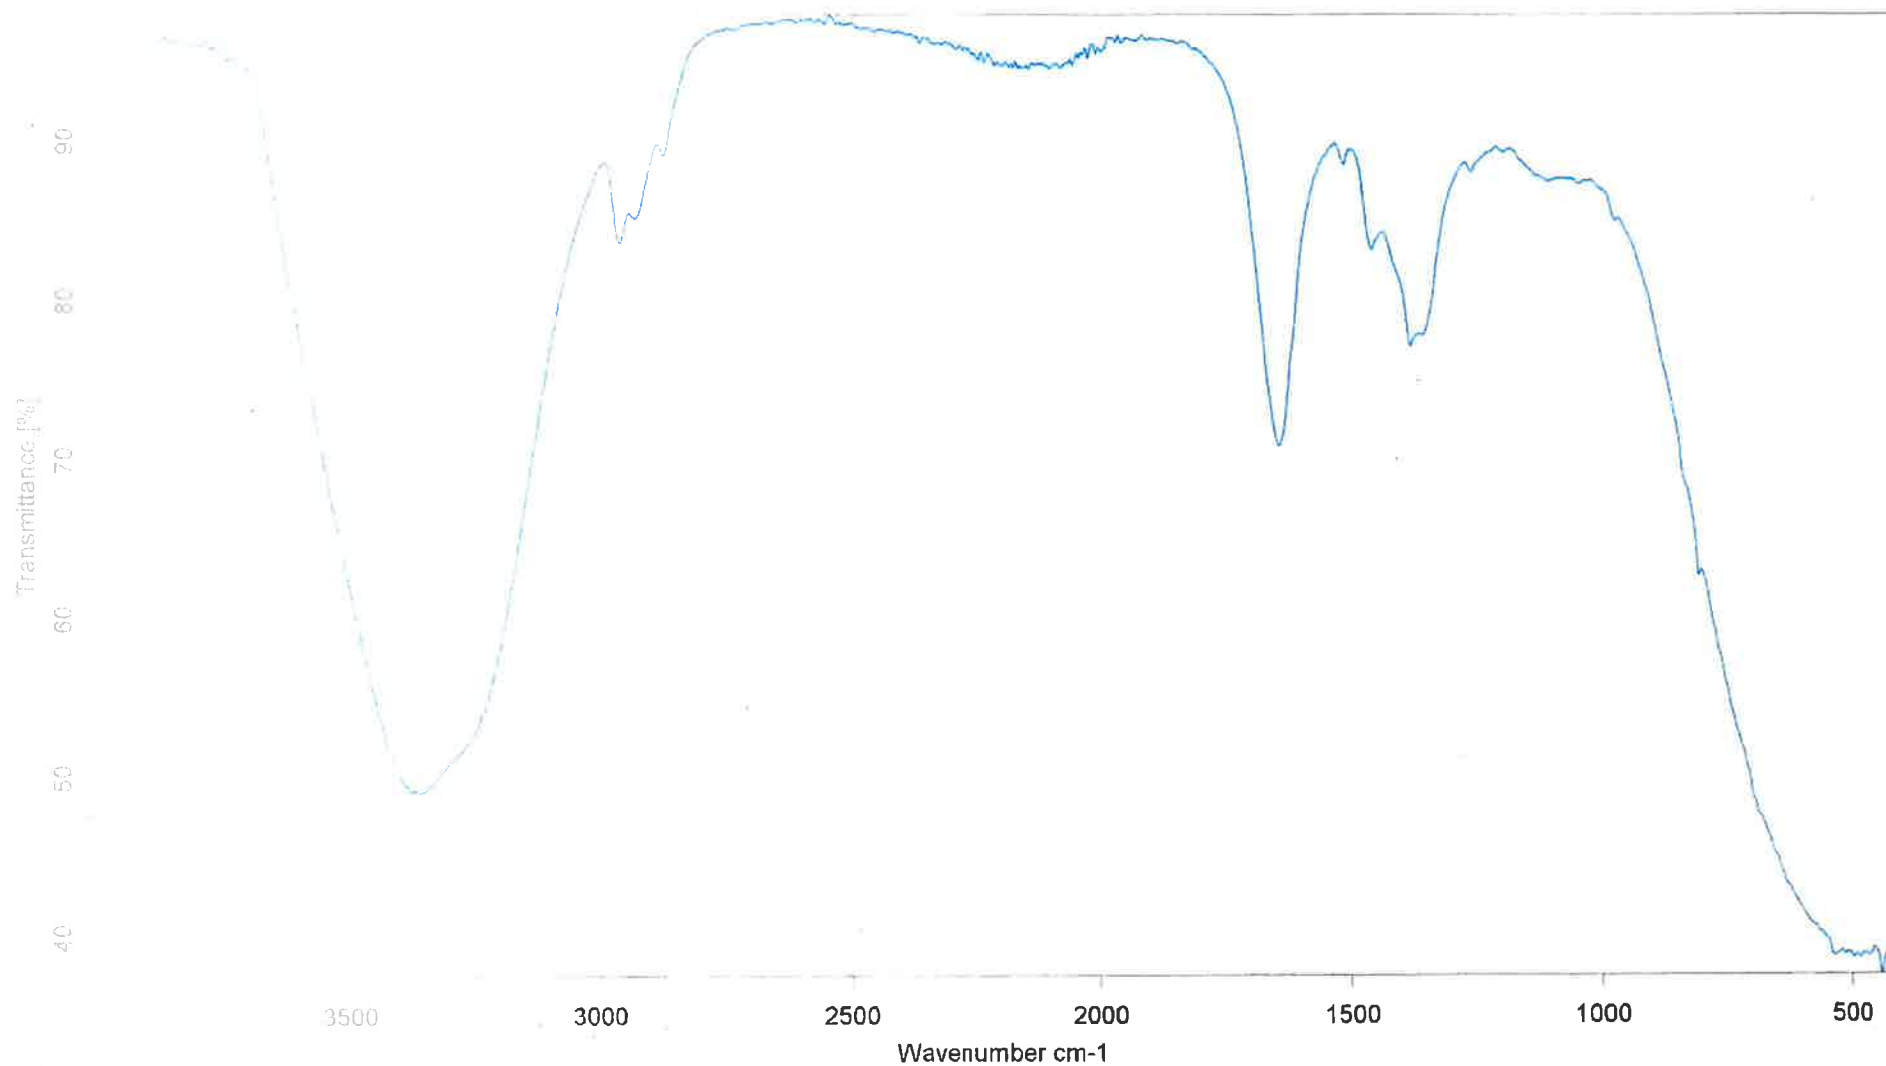

SN 339828 Evencure XDS Type 2 - Waterborne Hydrocarbon resin curing compound Rec- 29.06.26 Product Name : Concure X90 White Distributor : Parchem

NQ 03/08/21